



UNIVERSITI PUTRA MALAYSIA

**DEVELOPMENT OF MgZn-BASED FERRITE MATERIALS
FOR DEFLECTION YOKES**

THOR SOO FUNG

FSAS 2000 16

**DEVELOPMENT OF MgZn-BASED FERRITE MATERIALS
FOR DEFLECTION YOKES**

By

THOR SOO FUNG

**Thesis Submitted in Fulfilment of the Requirements for the Degree of
Master of Science in the Faculty of Science and Environmental Studies
Universiti Putra Malaysia**

June 2000



Abstract of the thesis presented to the Senate of Universiti Putra Malaysia in
fulfilment of requirements for the degree of Master of Science

**DEVELOPMENT OF MgZn-BASED FERRITE MATERIALS
FOR DEFLECTION YOKES**

By

THOR SOO FUNG

June 2000

Chairman : Associate Professor Dr. Mansor Hashim

Faculty : Faculty of Science and Environmental Studies

Ferrite materials in the form of the deflection yokes constitute a very significant portion of the entire world production of soft ferrites. The main applications are in TV sets and computer display monitors. Thus, this work was initiated to develop soft ferrite materials of the MgZn type suitable for use as deflection yoke materials. As cost plays a very important role in production, the initial part of the project was to develop the required material by manipulating the composition through production grade raw material. Various additives such as CaO, CuO, TiO₂ and La₂O₃ were added to assist in attaining the required properties. Green compacts with a sintering temperature of 1150°C and only air atmosphere were needed to achieve the magnetic and electrical properties close to those of SAMHWA's YL-5 material. A compositional design technique capable of producing deflection yokes material was

successfully developed to cater for the television and computer industry in Malaysia.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia bagi memenuhi keperluan Ijazah Master Sains.

**PENGHASILAN BAHAN FERIT MgZn UNTUK
"DEFLECTION YOKES"**

Oleh

THOR SOO FUNG

Jun 2000

Pengerusi : Professor Madya Dr. Mansor Hashim

Fakulti : Fakulti Sains dan Pengajian Alam Sekitar

Bahan ferit dalam bentuk "deflection yokes" merupakan sebahagian besar daripada pengeluaran ferit lembut dunia ini. Kegunaan utamanya ialah dalam peti TV dan monitor komputer. Maka, kerja ini dijalankan semata-mata untuk menghasilkan bahan ferit lembut jenis MgZn yang sesuai digunakan sebagai bahan "deflection yokes". Disebabkan, kos memainkan suatu peranan yang penting dalam pengeluaran, penyelidikan ini dimulakan dengan tujuan untuk menghasilkan bahan tersebut melalui manipulasi komposisi dengan menggunakan bahan mentah gred pengeluaran. Berbagai jenis bahan penambah seperti CaO, CuO, TiO₂ dan La₂O₃ telah digunakan untuk membantu dalam mendapatkan ciri-ciri yang dikehendaki. "Kompak hijau" dengan suhu persinteran setinggi 1150°C dan hanya udara atmosfera diperlukan untuk mencapai ciri-ciri magnet dan elektrik yang hampir dengan bahan ferit lembut SAMHWA YL-5. Suatu teknik rekabentuk komposisi yang berupaya

menghasilkan bahan ferit "deflection yokes", yang mampu memenuhi keperluan industri televisyen dan komputer di Malaysia, telah berjaya dihasilkan.

ACKNOWLEDGEMENTS

Firstly, I would like to extend my deepest gratitude and appreciation to my supervisor, Associate Professor Dr. Mansor Hashim for giving me the platform to pursue my studies and also the opportunity to explore the '*insights*' of ferrite science, besides the constant support throughout this work. I would also like to extend my gratitude to both my co-supervisors, Associate Professor Dr. Chow Sai Pew and Dr. Jumiah Hassan for guiding me through resistivity and surface analysis during my studies.

Special thanks to Puan Noorhana Yahya and Fanny Chin for their invaluable advice, constant encouragement and suggestions during my course of studies. I would also like to thank all my coursemates, friends and housemates who had rendered their help in one way or another towards the completion of this project.

Finally, I wish to express my sincere appreciation to my family who has been very supportive and understanding.


I certify that an Examination Committee met on 16 June 2000 to conduct the final examination of Thor Soo Fung on her Master of Science thesis entitled "Development of MgZn-Based Ferrite Materials for Deflection Yokes" in accordance with Universiti Pertanian Malaysia (Higher Degree) Act 1980 and Universiti Pertanian Malaysia (Higher Degree) Regulations 1981. The Committee recommends that the candidate be awarded the relevant degree. Members of the Examination Committee are as follows :

SALLEH HARUN, Ph.D
Associate Professor,
Faculty of Science and Environmental Studies
Universiti Putra Malaysia
(Chairman)

MANSOR HASHIM, Ph.D
Associate Professor,
Faculty of Science and Environmental Studies
Universiti Putra Malaysia
(Member)

CHOW SAI PEW, Ph.D
Associate Professor,
Faculty of Science and Environmental Studies
Universiti Putra Malaysia
(Member)

JUMIAH HASSAN, Ph.D
Faculty of Science and Environmental Studies
Universiti Putra Malaysia
(Member)

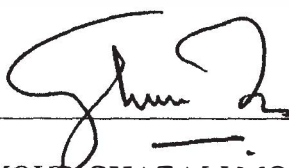

MOHD GHAZALI MOHAYIDIN, Ph.D
Professor/Deputy Dean of Graduate School,
Universiti Putra Malaysia

Date: 26 JUN 2000


This thesis submitted to the Senate of Universiti Putra Malaysia and was accepted as fulfilment of the requirements for the degree of Master of Science.



KAMIS AWANG, Ph.D,
Associate Professor
Dean of Graduate School,
Universiti Putra Malaysia

Date: **13 JUL 2000**

I hereby declare that the thesis is based on my original work except for quotations and citations which have been duly acknowledged. I also declare that it has not been previously or concurrently submitted for any other degree at UPM or other institutions.



THOR SOO FUNG

Date: 18 JUNE, 2000 .

TABLE OF CONTENTS

	Page
ABSTRACT	ii
ABSTRAK	iv
ACKNOWLEDGEMENTS	vi
APPROVAL SHEETS	vii
DECLARATION FORM	ix
LIST OF TABLES	xii
LIST OF FIGURES	xiii
LIST OF PLATES	xv
LIST OF SYMBOLS AND ABBREVIATIONS	xvi
 CHAPTER	
 I INTRODUCTION	 1
General	1
Application as magnetic deflection yoke	2
Historical overview	3
Significance of the study	4
Statement of objective	4
Future technology of ferrites	5
 II LITERATURE REVIEW	 7
Introduction	7
Chemical aspects of ferrites	8
Microstructural aspects of ferrites	16
 III THEORY	 19
Introduction	19
Spinel ferrite	19
Site preferences of the ions	20
Ferrimagnetism in spinel ferrite	22
Domains and hysteresis	24
Magnetic properties of ferrite	27
Intrinsic properties	27
Extrinsic properties	30
Magnetic losses	34
Electrical properties of ferrite	37



IV	METHODOLOGY	41
	Introduction	41
	Procedure of work	41
	Laboratory processes	43
	Sample preparation	43
	Raw materials	43
	Mixing	45
	Presintering	46
	Granulation	47
	Moulding	48
	Sintering	49
	Experimental measurement	51
	Initial permeability and magnetic losses	51
	Initial permeability, μ_i	52
	Magnetic losses	52
	Curie temperature	53
	Resistivity, ρ	54
	Hysteresis parameters	54
	Linear shrinkage	55
	Density	55
	Microstructure Analysis	56
V	RESULTS AND DISCUSSION	59
	Development 1: $\text{Mg}_{0.5}\text{Zn}_{0.5}\text{Fe}_2\text{O}_4$ with CaO additions	61
	Development 2: M series	65
	Development 3: C series	69
	Development 4: R series	75
	Development 5: $\text{Mg}_{0.5}\text{Cu}_{0.1}\text{Zn}_{0.44}\text{Fe}_{1.92}\text{O}_{3.92}$ with TiO_2 additions	87
	Development 6: $\text{Mg}_{0.5}\text{Cu}_{0.1}\text{Zn}_{0.44}\text{La}_x\text{Fe}_{1.92-x}\text{O}_{3.92\pm\delta}$	93
VI	CONCLUSION	110
	Summary of main findings	110
	Suggestions	112
	BIBLIOGRAPHY	114
	APPENDICES	121
	VITA	126

LIST OF TABLES

Table		Page
2.1	Tendencies of Metal Oxides to Produce Exaggerated Grain Growth	12
3.1	Radii of Metal Ions Involved in Spinel Ferrite	21
3.2	Radii of Tetrahedral and Octahedral Sites in Some Ferrites	21
3.3	Magnetic Moments of Some Simple Ferrites (μ_B)	23
5.1	Experimental measurements of $Mg_{0.5}Zn_{0.5}Fe_2O_4$ with CaO additions	61
5.2	Saturation magnetization and Curie Temperature values for $Mg_{0.45-x}Cu_{0.05+x}Zn_{0.50}Fe_2O_4$	66
5.3	Experimental measurements of $Mg_{0.50}Cu_{0.05+x}Zn_{0.45-x}Fe_2O_4$	70
5.4	Experimental measurements of $Mg_{0.50}Cu_{0.10}Zn_{0.40+x}Fe_{2-2x}O_{4-2x}$	85
5.5	Experimental measurements of $Mg_{0.5}Cu_{0.1}Zn_{0.44}Fe_{1.92}O_{3.92}$ with TiO_2 additions. (Sample T0 to T5)	88
5.6	Measured Properties of Materials YL-5 and L5	108

LIST OF FIGURES

Figure		Page
2.1	Saturation Magnetic Moment of Various Ferrites Diluted with Zinc Ferrite	9
2.2	Variation of (••) Initial Permeability μ_i , (-+-) Q Value and (-*-) $\mu_i Q$ Product with La^{3+} Concentration	13
2.3	The Variation of Resistivity with Iron Content, x, in Ni-ferrites of Composition $\text{Ni}_{0.3}\text{Zn}_{0.7}\text{Fe}_x\text{O}_4$	15
2.4	Permeability of MnZn Ferrite as a Function of Grain Size in Microns	17
3.1	Two Octants of Spinel Unit Cells	20
3.2	A Typical Hysteresis Loop of Ferrite	25
3.3	Typical μ_i^* - Frequency Spectrum Shows Magnetic Rotation Resonance, Domain Wall Relaxation and Diffusional Relaxation Processes.	36
4.1	A Schematic Flow Chart of the Compositional Design Techniques	42
4.2	Flow Chart for Sample Preparation	44
4.3	Archimedes Method	55
5.1	Initial permeability for $\text{Mg}_{0.45-x}\text{Cu}_{0.05+x}\text{Zn}_{0.50}\text{Fe}_2\text{O}_4$ vs CuO content	67
5.2	Resistivity for $\text{Mg}_{0.45-x}\text{Cu}_{0.05+x}\text{Zn}_{0.50}\text{Fe}_2\text{O}_4$ vs CuO content	67
5.3	Initial permeability vs mole fraction of ZnO in $\text{Mg}_{0.50}\text{Cu}_{0.05+x}\text{Zn}_{0.45-x}\text{Fe}_2\text{O}_4$ (Sample C1 to C4)	70
5.4	Bulk Density and Theoretical Density for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.40+x}\text{Fe}_{2-2x}\text{O}_{4-2x}$ (Sample R1 to R8)	76
5.5a	Resistivity for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.40+x}\text{Fe}_{2-2x}\text{O}_{4-2x}$	77

Figure		Page
5.5b	Resistivity for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.40+x}(\text{Fe}_2\text{O}_4)_{0.90-x}$	78
5.6	Initial Permeability for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.40+x}\text{Fe}_{2-2x}\text{O}_{4-2x}$ (Sample R1 to R8)	80
5.7	Relative Loss Factor for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.40+x}\text{Fe}_{2-2x}\text{O}_{4-2x}$ (Sample R1 to R8)	83
5.8	Initial Permeability for $\text{Mg}_{0.5}\text{Cu}_{0.1}\text{Zn}_{0.44}\text{Fe}_{1.92}\text{O}_{3.92}$ with TiO_2 additions. (Sample T0 to T5)	89
5.9	Resistivity for $\text{Mg}_{0.5}\text{Cu}_{0.1}\text{Zn}_{0.44}\text{Fe}_{1.92}\text{O}_{3.92}$ with TiO_2 additions. (Sample T0 to T5)	90
5.10	Relative Loss Factor for $\text{Mg}_{0.5}\text{Cu}_{0.1}\text{Zn}_{0.44}\text{Fe}_{1.92}\text{O}_{3.92}$ with TiO_2 additions. (Sample T0 to T5)	91
5.11	Average Grain Size for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.44}\text{La}_x\text{Fe}_{1.92-x}\text{O}_{3.92\pm\delta}$ (Sample L1 to L5)	94
5.12a	Resistivity for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.44}\text{La}_x\text{Fe}_{1.92-x}\text{O}_{3.92\pm\delta}$ (Sample L1 to L5)	95
5.12b	Resistivity for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.44}\text{La}_x\text{Fe}_{1.92-x}\text{O}_{3.92\pm\delta}$ (Sample L1 to L5)	95
5.13	Initial Permeability for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.44}\text{La}_x\text{Fe}_{1.92-x}\text{O}_{3.92\pm\delta}$ (Sample L1 to L5)	97
5.14	Relative Loss Factor for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.44}\text{La}_x\text{Fe}_{1.92-x}\text{O}_{3.92\pm\delta}$ (Sample L1 to L5)	100
5.15	Q value for $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.44}\text{La}_x\text{Fe}_{1.92-x}\text{O}_{3.92\pm\delta}$ (Sample L1 to L5)	101
5.16	Curie Temperature of $\text{Mg}_{0.50}\text{Cu}_{0.10}\text{Zn}_{0.44}\text{La}_x\text{Fe}_{1.92-x}\text{O}_{3.92\pm\delta}$ (Sample L1 to L5)	107

LIST OF PLATES

Plate		Page
1	Milling Machine	45
2	Electric Furnace	47
3	Mould	48
4	Pressing Machine	49
5	Cutting Machine	57
6	Polishing Mchine	57
7	Micrographs of $Mg_{0.5}Zn_{0.5}Fe_2O_4$ with 0.50 and 0.53 wt% of CaO additions	64
8	Micrographs of $Mg_{0.5}Cu_{0.1}Zn_{0.4}La_{0.01}Fe_{1.91}O_{3.92\pm\delta}$ (Sample L4)	105
9	Micrographs of $Mg_{0.5}Cu_{0.1}Zn_{0.4}La_{0.03}Fe_{1.89}O_{3.92\pm\delta}$ (Sample L5)	106

LIST OF SYMBOLS AND ABBREVIATIONS

A	cross sectional area
H	applied field
H_C	coercive force
μ_B	Bohr magneton
T_C	Curie temperature
ρ	resistivity
f	frequency
μ'	real of permeability or magnetic loss
μ''	imaginary part of permeability or magnetic loss
B	induction
L	inductance
μ_i	initial permeability
μ_0	magnetic constant
D_i	inner diameter
σ	internal stress
l	length
$\tan \delta$	loss tangent
N	number of wire turns
D_0	outer diameter
PVA	polyvinyl alcohol
Q	quality factor
RLF	relative loss factor

B_r	remanence induction
B_s	saturated induction
M_s	saturation magnetisation
T	temperature
t	thickness
K_1	first anisotropy constant
W	weight
SEM	scanning electron microscope

CHAPTER I

INTRODUCTION

General

Ferrimagnetism is the term proposed by Neel to describe the magnetism of ferrites whereby the material possesses unequal, anti parallel ionic magnetic moments resulting in a net moment due to incomplete compensation. This spontaneous magnetization is temperature dependent and vanishes at the Curie temperature.

Ferrites are generally divided into two major classes, the soft and the hard ferrites which are further classified according to their specific crystal structure; cubic spinel, garnet and magnetoplumbite (Goldman, 1990).

Soft magnetic materials are generally developed with technical applications in view as they become magnetized in relatively weak fields and return to a state of relatively low residual magnetism when the field is removed. Besides, the remarkably high electrical resistivity of these materials, depending on composition, has given ferrites a distinct advantage as magnetic materials of choice in most technological applications covering antennas,

transformer cores, deflection yokes and others. In addition, the spinel crystal structure of ferrites is tolerant to numerous variations in their chemical composition, giving the technologist access to a wide range of properties.

Application As Magnetic Deflection Yoke

Through the years, the demand in terms of tonnage has steadily increased but also the specific applications of ferrite have changed remarkably and kept pace with the developments in electronic technologies. At this time, the TV industry still remains the largest user of ferrites with approximately 1 kg of ferrites per TV set (Ghate, 1981) with deflection yokes contributing about 20% of applications.

A television picture tube uses magnetic fields that are produced by external coils placed around the neck of the picture tube for deflecting the beam vertically and horizontally. The combination of the vertical and horizontal deflection coils plus the core is called the yoke. These coils have flowing through them a sawtooth current and the magnetic field generated by this flow of energy through the coil will influence the beam and deflect it accordingly. The horizontal deflection coil that sweeps the beam across the face of the tube from left to right is split into 2 sections and mounted above and below the tube neck. The vertical deflection coil is also split into 2 sections and mounted on each side of the tube neck in order to pull the beam

gradually downward as the horizontal coils sweep the beam across the tube face.

Historical Overview

The existence of magnetite, a typical ferrimagnetic ferrite called lodestone, has been known since more than 2000 years ago. Nevertheless, there was hardly any progress in scientific research concerning ferrites until the 19th century (Ishino, 1987). Ferrites came into prominence at the end of the Second World War (Goldman, 1990).

In 1930, Y. Kato and T. Takei discovered soft ferrite from the solid solution of zinc ferrite. Based on their research, Snoek (1936) and his coworkers at the Philips Research Laboratories in the Netherlands developed the first soft magnetic spinel ferrites for commercial applications under the trade name Ferroxcube. In 1948, the first explanatory theories on the origin of magnetism (theory of ferrimagnetism) in ferrites was published by Neel. This has brought about a great advance in the magnetic investigation of ferrites.

The real breakthrough, however, of ferrites as important materials for electrotechnical applications took place in the early 1950s due to the large-scale introduction of the television (Owens, 1956). From 1955 to 1965, when ferrites were first applied to electron beam deflection, Mn-Zn or Ni-Zn ferrites

were used. Providing lower resistance, Mn-Zn ferrites were used with saddle toroidal winding. But due to ringing problems, they were gradually replaced by Ni-Zn ferrites, which featured higher resistance. Currently, Japanese, Korean and Taiwanese makers mainly select Mg-Zn ferrites for their low material costs.

Significance of the Study

Today, there is a growing need for ferrite materials in the form of the deflection yokes as the main applications are in TV sets and computer display monitors, both being in the upper part of the technology and having a huge market. However, production of deflection yokes is dominated by only a few big manufacturers such as TDK and SAMWHA. Therefore the aim of this project is to produce deflection yoke materials which are not only superior in qualities but also lower in cost. It is hoped that the results of this research development work will be a significant contribution to the television and computer industry in Malaysia.

Statement of Objective

The objective of this project is to develop soft ferrite materials of the MgZn type suitable for use as deflection yoke cores with specific characteristic and properties similar to those of SAMHWA deflection yoke cores.

The ultimate objective is to obtain a relatively large saturation magnetization, B_{sat} , as it provides a large excursion of flux and thus it is able to handle faster raster rate. Besides, since TVs operate with a large amount of electric power, it is necessary to produce a low-loss ferrite at high flux densities to reduce heat generation and to ensure greater safety. Therefore, high electrical resistivity plays an important role as it minimizes the eddy current losses and also eliminates the need for taped insulation between yoke and winding.

Future Technology Of Ferrites

If the trends in magnetic materials is examined as a whole, ferrites will continue to play a unique role by virtue of their high electrical resistivity, ease of fabrication into a multitude of shapes having widely divergent properties, light weight and cost effectiveness. It is expected that development of future process technologies will be evolutionary as the technological developments in ferrites have been basically evolutionary rather than revolutionary. Material science and technology has been steadily applied to improve properties as well as new products. However, the highly capital intensive nature of ferrite processing makes it that much more difficult to readily implement changes, especially in products used in large quantities or requiring a large volume of material.

Ferrites will make a remarkable progress towards the future as an advanced ceramics as it still has promising opportunities for dramatic developments in the fundamental studies, search for new materials, improvements in manufacturing technology and the search for new applications (Sugitomo, 1985).

CHAPTER II

LITERATURE REVIEW

Introduction

Despite of the utilisation of ferrite core decades ago, commercialisation of MgZn based ferrite replacing MnZn and NiZn ferrite has been very recent. Hence, the scarcity of publications exist. Besides, due to the great competition in the ferrite market, reputable manufacturers such as TDK, SAMHWA and Philips tend to conceal the compositional and processing details that contribute to high quality ferrite products. Fortunately, there still exists a wide availability of open publications on fundamental science and applied aspects in this field. Thus, these perhaps would be the only source of knowledge to researchers in fabricating high-quality ferrite materials and products comparable with those available on the world market.

Although not much has been studied on MgZn ferrite, the ample literature particularly on NiZn and MnZn ferrites available may be helpful in understanding the properties of ferrites in this project. In general, the literature review is divided into two sections based on the chemical and microstructural aspects of ferrites.